



FIG.1

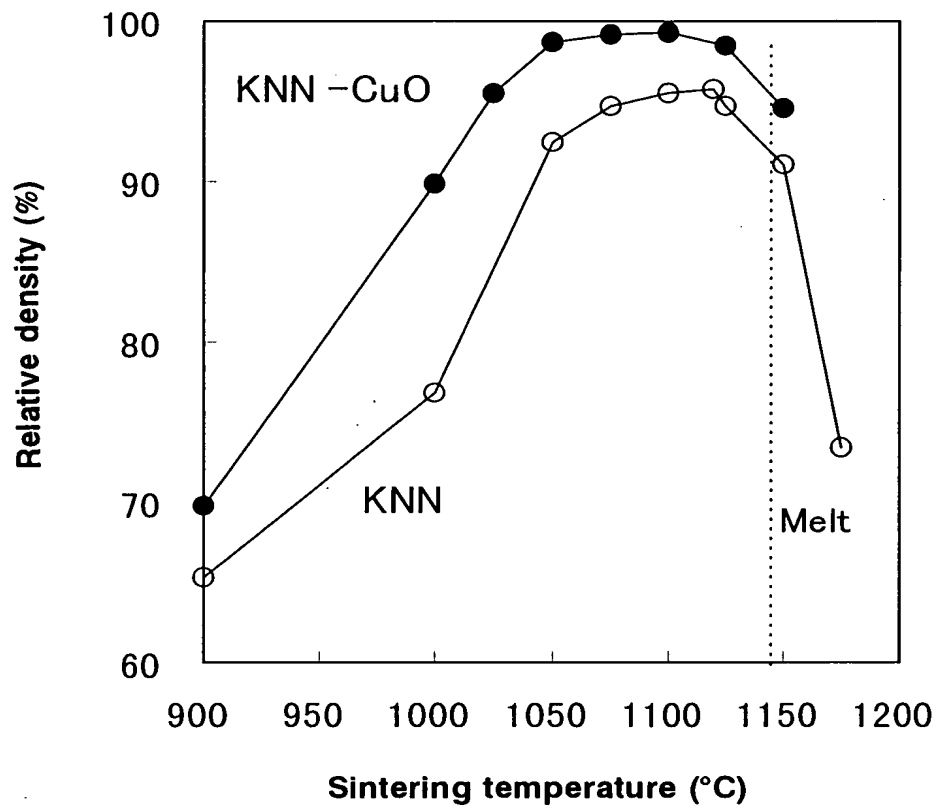

KNN : $K_{0.5}Na_{0.5}NbO_3$

KNN - CuO : $K_{0.5}Na_{0.5}NbO_3$


FIG.2

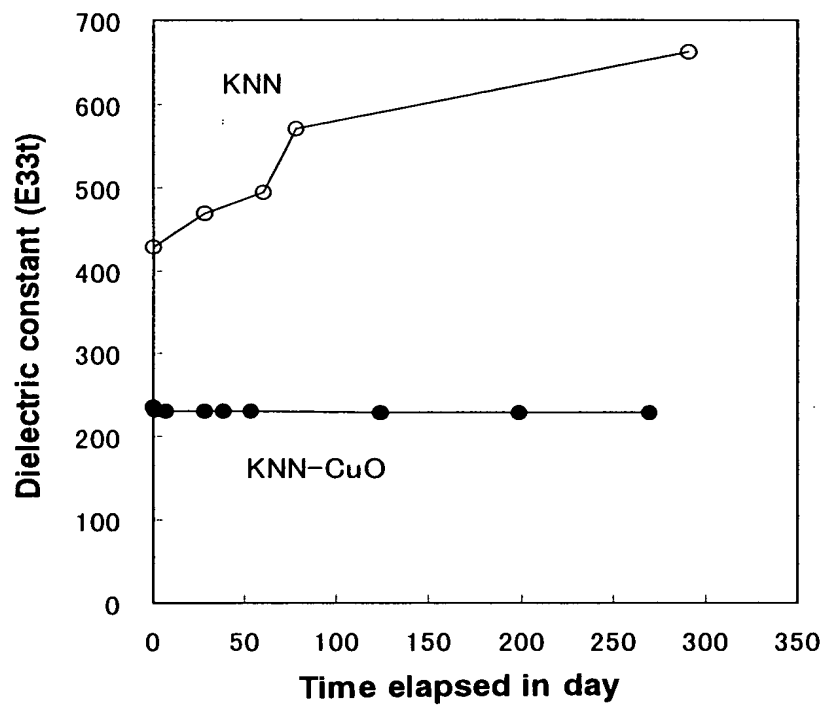

KNN : $K_{0.5}Na_{0.5}NbO_3$

KNN-CuO : $K_{0.5}Na_{0.5}NbO_3 + 1 \text{ mol\% CuO}$


FIG.3

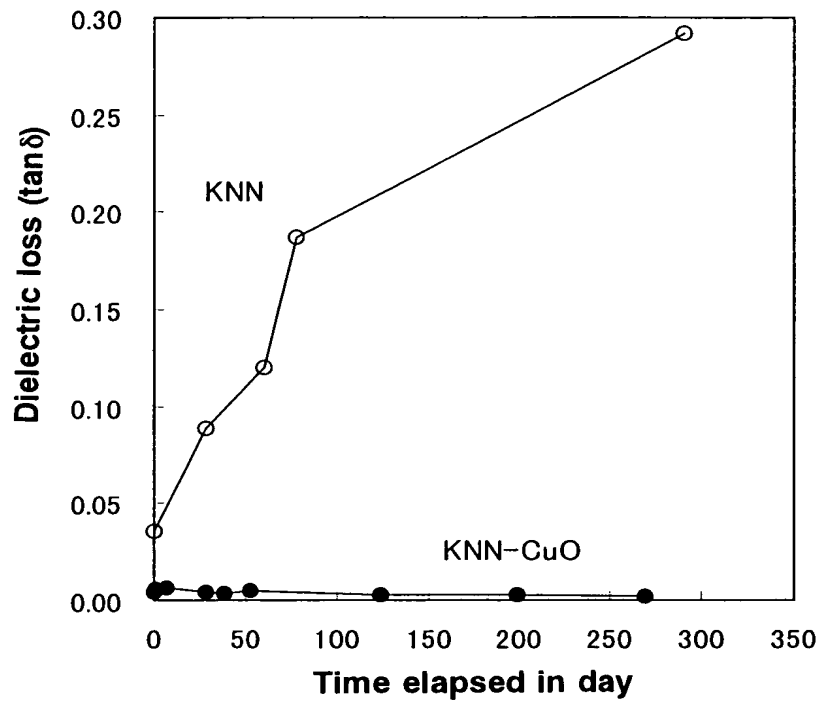

KNN : $K_{0.5}Na_{0.5}NbO_3$

KNN-CuO : $K_{0.5}Na_{0.5}NbO_3 + 1 \text{ mol\% CuO}$

FIG.4

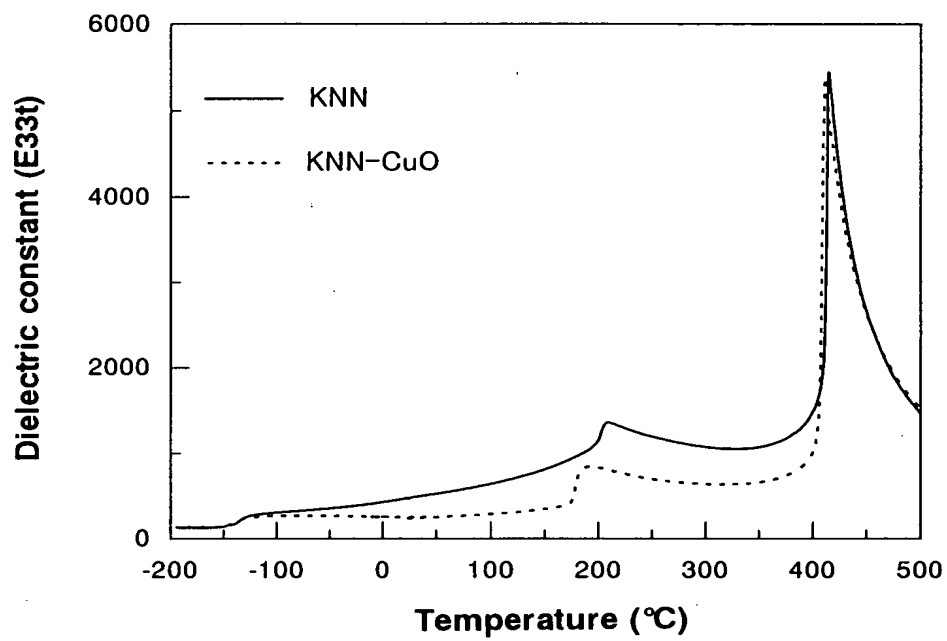

KNN : $(K_{0.5}Na_{0.5})NbO_3$

KNN-CuO : $(K_{0.5}Na_{0.5})NbO_3 + 1\text{mol\% CuO}$

FIG.5






FIG.6



KNN : $K_{0.5}Na_{0.5}NbO_3$ KNN-LT : $\{(K_{0.5}Na_{0.5})_{0.9}(Nb_{0.8}Ta_{0.2})O_3\}$

FIG.7

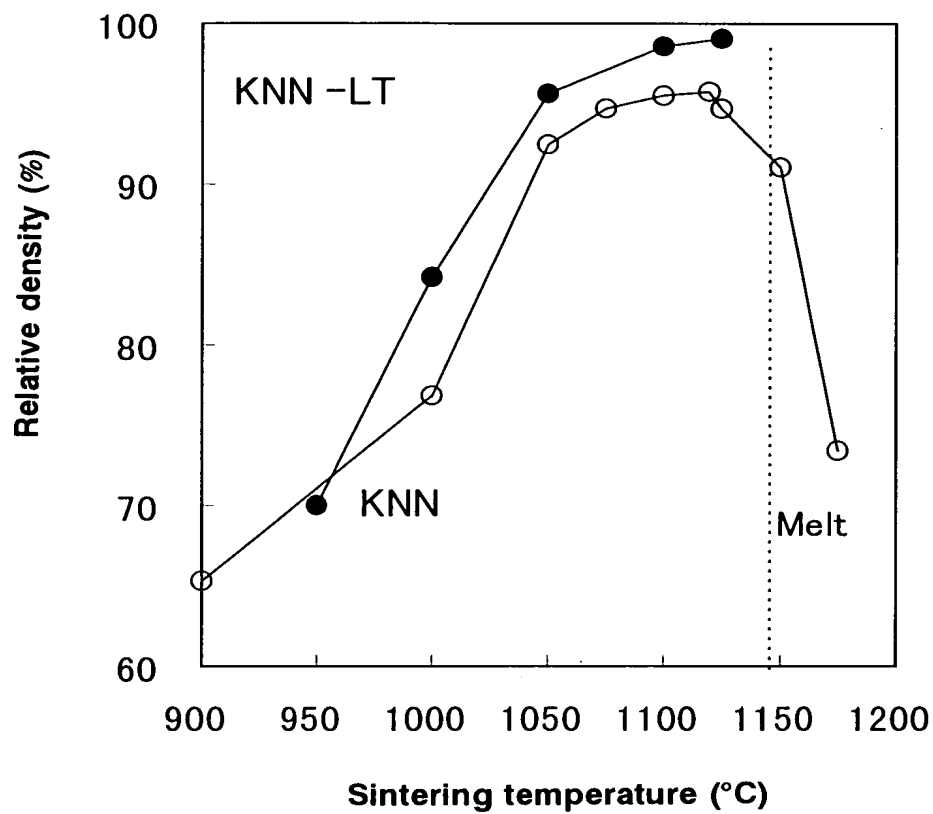

KNN : $K_{0.5}Na_{0.5}NbO_3$

KNN-LT : $[(K_{0.5}Na_{0.5})_{0.9}(Nb_{0.8}Ta_{0.2})O_3]$

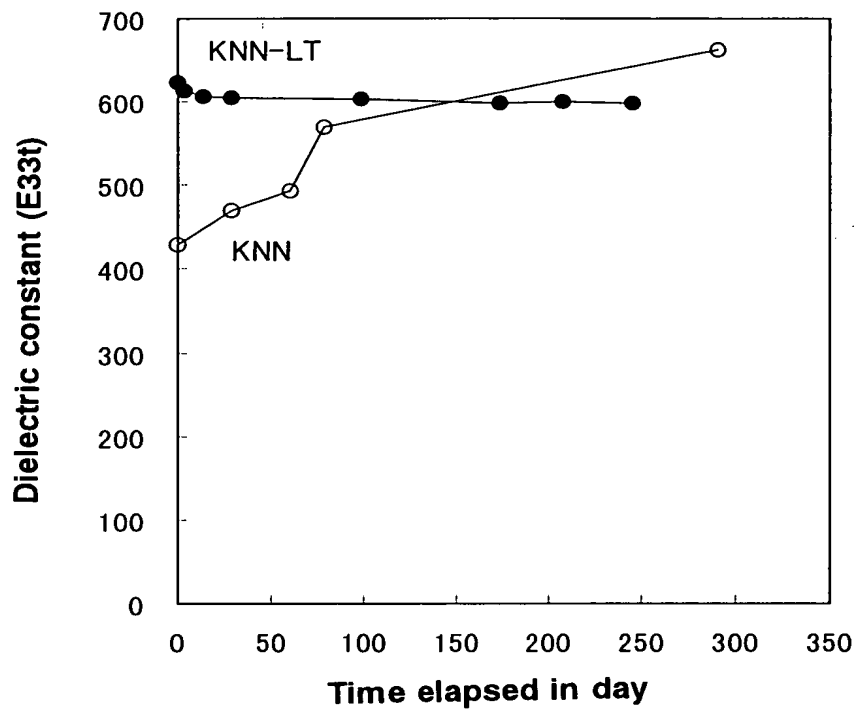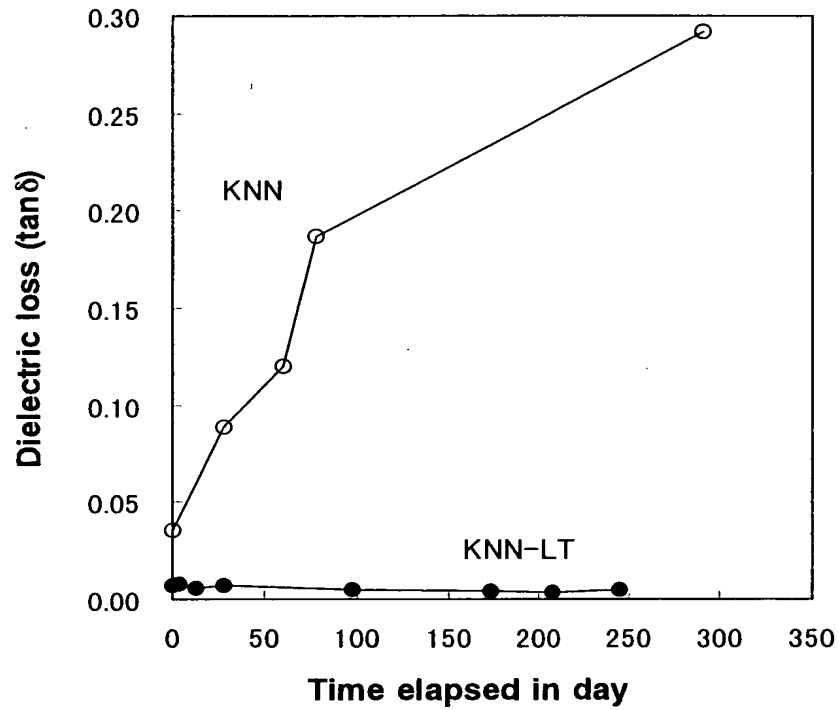FIG.8



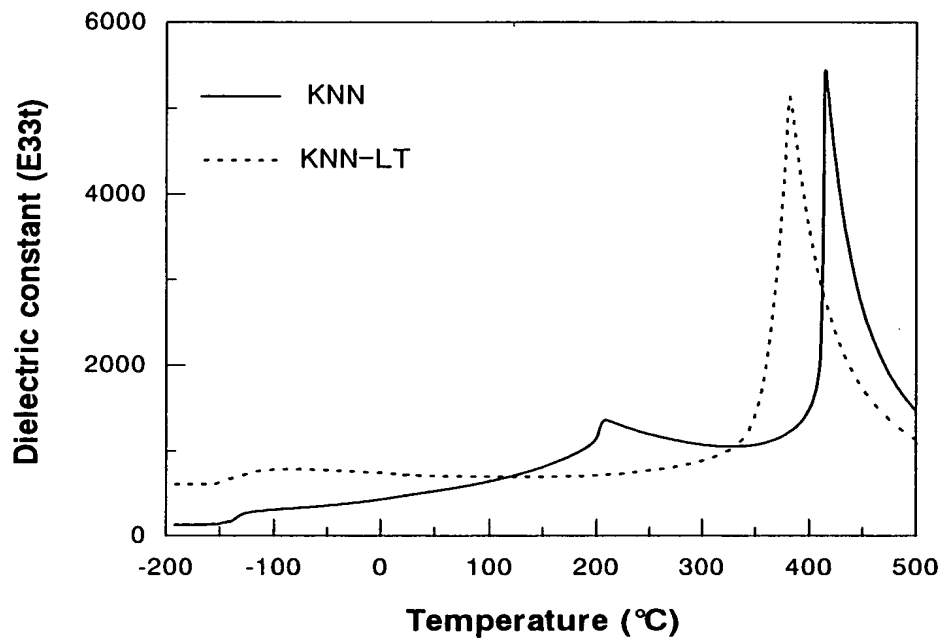


FIG.9(a)

Electromechanical coupling factors (kp)

20	0.092	0.170	0.187	0.150	0.160
15	0.087	0.203	0.230	0.209	0.204
10	0.151	0.292	0.307	0.292	0.283
8	0.196	0.340	0.335	0.313	0.287
6	0.332	0.415	0.383	0.406	0.336
4	0.371	0.456	0.501	0.431	0.382
2	0.469	0.395	0.341	0.380	0.330
0	0.334	0.453	0.465	0.332	0.294
	0	10	20	30	40

T a (mol%)

FIG.9(b)

Piezoelectric constant (d31 pm/V)

20	9.7	20.2	21.5	16.4	17.3
15	10.1	23.2	25.1	23.7	22.0
10	20.4	39.6	36.3	32.5	33.2
8	27.5	50.8	46.1	41.2	35.6
6	57.7	71.0	60.1	58.3	46.3
4	39.8	69.5	95.0	73.1	63.5
2	46.9	51.4	54.3	79.3	70.1
0	37.6	49.5	60.5	62.9	66.0
	0	10	20	30	40

T a (mol%)

FIG.9(c)

Piezoelectric constant (g31 10⁻³ Vm/N)

20	2.8	4.2	4.5	3.7	3.6
15	2.2	4.8	5.4	4.6	4.6
10	3.5	6.7	6.6	6.6	6.3
8	4.7	6.8	6.8	6.1	6.4
6	7.5	7.9	7.1	7.7	6.0
4	11.0	10.3	9.0	7.5	6.2
2	14.5	9.3	6.8	6.1	4.7
0	9.9	12.1	10.5	6.0	4.1
	0	10	20	30	40

T a (mol%)

FIG.10(a)

Curie point (°C)

20	505	459	390	347	295
15	502	450	385	337	280
10	499	450	380	330	262
8	485	420	363	310	250
6	474	405	345	295	235
4	460	393	337	279	220
2	435	375	308	250	192
0	415	350	285	233	168
	0	10	20	30	40

T a (mol%)

FIG.10(b)

Dielectric constant (E33t)

20	399	540	539	504	542
15	530	544	521	580	546
10	657	672	624	556	599
8	657	847	762	761	625
6	864	1014	959	855	868
4	409	763	1204	1106	1165
2	364	621	903	1466	1686
0	429	462	652	1187	1837
	0	10	20	30	40

T a (mol%)

FIG.10(c)

Dielectric loss (tan δ)

20	0.091	0.015	0.011	0.014	0.008
15	0.045	0.022	0.007	0.007	0.008
10	0.088	0.039	0.007	0.007	0.008
8	0.037	0.010	0.010	0.008	0.011
6	0.050	0.008	0.006	0.009	0.011
4	0.014	0.014	0.008	0.006	0.014
2	0.003	0.023	0.018	0.016	0.018
0	0.036	0.005	0.010	0.012	0.009
	0	10	20	30	40

T a (mol%)